

# 50% Design Report for the Use of Carbonated Cement Kiln Dust as Soil Stabilization Amendment

NORTHERN  
ARIZONA  
UNIVERSITY®



## **Team K.V.S.C**

Abdullah Alqattan  
Mohammad Alhulaila  
Mohammad Altarkait  
Tung Do

**CENE486C-1 – Spring 2017**

Instructor: Alarick Reiboldt

## Acknowledgements

The completion of this Capstone project on the use of Carbonated Cement Kiln Dust as a soil stabilization amendment could not have been possible without the participation and assistance of so many people. Their contributions are sincerely appreciated and gratefully acknowledged.

The project team would like to specifically express the appreciation and indebtedness to professor Alarick Reiboldt and lab manager Gerjen Slim at the Engineering Department of Northern Arizona University for endless support on this Capstone project; and professor Pranshoo Solanki from Illinois State University for his previous study on Engineering Properties and Moisture Susceptibility of Silty Clay Stabilized with Lime, Class C Fly Ash, and Cement Kiln Dust.

# Table of Contents

Acknowledgements.....	i
Table of Contents.....	ii
Table of Tables.....	iv
Table of Figures.....	v
1.0 Project Understanding.....	1
1.1 Project Purpose.....	1
1.2 Project Background.....	1
1.3 Technical Considerations.....	1
1.4 Project Constraints.....	2
1.4.1 CKD/CCKD Variability.....	2
1.4.2 Soil Variability.....	2
1.4.3 Laboratory Soils Testing.....	2
1.5 Stakeholders.....	2
1.5.1 The Client.....	2
1.5.2 Cement Manufacturing Companies.....	2
1.5.3 Construction Companies.....	3
1.5.4 Global Community.....	3
1.6 Scope of Services.....	3
Task 1.0: Literature Review.....	3
Task 2.0: Soil Selection.....	3
Task 3.0: Preparing Soil Samples.....	4
Task 4.0: Soil Strength Test.....	5
Task 5.0: Analysis Results.....	5
Task 6.0: Project Management.....	5
1.7 Exclusions.....	6
2.0 Technical Sections.....	7
2.1 Literature Review.....	7

2.2	Soil Selection .....	8
2.2.1	Determining Soil Used.....	8
2.2.2	Obtaining Soil Samples.....	8
2.2.3	Soil Classification.....	9
2.3	Preparing Soil Mixtures.....	12
2.3.1	Determining Amount of Mixtures.....	12
2.3.2	Obtaining Lime, CKD and CCKD.....	13
2.3.3	Preparing Soil Mixtures.....	13
2.4	Soils Testing.....	13
2.4.1	Proctor Compaction .....	14
2.4.2	Direct Shear.....	14
2.4.3	Triaxial Shear: Unconsolidated Undrained .....	14
2.5	Analysis Results .....	14
2.6	Project Management .....	14
3.0	References .....	15
4.0	Appendices.....	16
	Appendix A: Sieve Analysis's Data on Raw Soil #1 .....	16
	Appendix B: Sieve Analysis's Data on Raw Soil #2 .....	17
	Appendix C: Sieve Analysis's Data on Raw Soil #3 .....	18
	Appendix D: Atterberg Limit Tests' Data .....	19
	Appendix E: Engineered Soil #1 .....	20
	Appendix F: Engineered Soil #2 .....	21
	Appendix G: Engineered Soil #3.....	22
	Appendix H: Stoichiometry Analysis .....	23
	Appendix I: Proctor Test #1.....	24
	Appendix J: Proctor Test #2 .....	25
	Appendix K: Proctor Test #3.....	26

## Table of Tables

Table 1.1: Mixture Plan.....	4
Table 1.2: Project Schedule.....	6
Table 2.1: Information on Soils used in Previous Study [4] .....	7
Table 2.2: Average Percent Finer (PSD) .....	9
Table 2.3: Average Liquid Limit.....	10
Table 2.4: Average Plastic Limit .....	10
Table 2.5: Engineered Soil's Average PSD .....	11
Table 2.6: CKD Chemical Components.....	12
Table 2.7: Amount of Lime. CKD and CCKD needed to add .....	13
Table 2.8: Total Amounts Needed .....	13
Table 2.9: Proctor Tests' Results .....	14
Table 4.1: Data Soil #1.....	16
Table 4.2: Data Soil #2.....	17
Table 4.3: Data Soil #3.....	18
Table 4.4: Plastic Limit Data .....	19
Table 4.5: Liquid Limit Data .....	19
Table 4.6: Engineered Soil #1.....	20
Table 4.7: Engineered Soil #2.....	21
Table 4.8: Engineered Soil #3.....	22
Table 4.9: Stoichiometry Analysis .....	23
Table 4.10: Proctor Test #1 .....	24
Table 4.11: Proctor Test #2 .....	25
Table 4.12: Proctor Test #3 .....	26

## Table of Figures

Figure 2.1: Silt-Rich Sediment Site .....	8
Figure 2.2: Average PSD Graph .....	9
Figure 2.3: Engineered Soil's Average PSD Graph.....	11
Figure 4.1: PSD Soil #1.....	16
Figure 4.2: PSD Soil #2.....	17
Figure 4.3: PSD Soil #3.....	18
Figure 4.4: Liquid Limit Graph.....	19
Figure 4.5: PSD Engineered Soil #1 .....	20
Figure 4.6: PSD Engineered Soil #2 .....	21
Figure 4.7: PSD Engineered Soil #3 .....	22
Figure 4.8: Compaction Curve #1.....	24
Figure 4.9: Compaction Curve #2.....	25
Figure 4.10: Compaction Curve #3.....	26

## 1.0 Project Understanding

### 1.1 Project Purpose

The project purpose is to determine the effectiveness of Carbonated Cement Kiln Dust for use as a soil stabilization amendment. Cement is one of the most Carbon intensive materials to produce. One of the by-products of the cement manufacturing process is Cement Kiln Dust (CKD). Adding gaseous Carbon Dioxide under the right conditions to CKD will form Carbonated Cement Kiln Dust (CCKD). One potential use of CCKD is as a stabilizing amendment for compacted soils. As of now, CCKD is not put in use. By conducting this study, the project team will determine the efficacy of CCKD as a stabilizer for soils.

### 1.2 Project Background

Carbonated Cement Kiln Dust (CCKD) has a potential use as stabilizer for soils due to its chemical components (mainly composed of Carbonated Calcium). The project team will conduct tests as requested by the client to determine if CCKD can be used as a stabilizer. Lime and Cement Kiln Dust have been proven to be usable to improve soil strength. Therefore, the project team will compare the results of tests on CCKD with the results of the same tests on CKD and lime to determine the efficacy of CCKD as a stabilizer for soils. Moreover, CCKD is made from CKD, which is currently treated as waste by Cement Manufacturer, and Carbon Dioxide  $\text{CO}_2$ . By proving the use of CCKD as soil stabilization amendment, the project team can help reduce the CKD waste and a part of  $\text{CO}_2$  emission due to Cement manufacturing process, which is accounted to approximately 5% of Carbon Dioxide  $\text{CO}_2$  emission that human produced [1].

### 1.3 Technical Considerations

Many previous studies indicated that lime and CKD could be used as soil stabilizers. For example, Little (2000) reported that the long-term effect of lime stabilization on fine grained soils, encountered in Texas, induces a 1,000% or more increase in resilient modulus ( $M_r$ ) over that of the untreated soil. The AASHTO T274 method was used to determine the resilient modulus values. Values of  $M_r$  typically falls within a range of 210 and 3,500 MPa. The strength values determined for lime- stabilized soil was reported as high as 7,000 to 10,000 kPa. TST was also performed to evaluate the moisture susceptibility on 7-day cured specimens [2]. In another the study by Parsons and Kneebone (2004), eight different soils with classifications of CH, CL, ML, SM, and SP were tested for strength, swell and durability to evaluate the relative performance of CKD as a stabilizing stabilizer. Results were compared with previous findings for the same soils stabilized with lime, cement, and fly ash. Substantial increase in strength and decrease in swell was found with the addition of CKD. CKD treated soil samples were also reported to have a performance in wet-dry testing that is similar to that for lime, fly ash and cement treated soil [3].

Because CCKD contains mainly lime, therefore, CCKD also has potential to be used as a soil stabilizing amendment.

## **1.4 Project Constraints**

When conducting the study, the project team determined that the following problems would be the potential limitations for the project: CKD/CCKD Variability; Soil Variability; and Laboratory Soils Testing.

### **1.4.1 CKD/CCKD Variability**

The composition of CKD/CCKD is a challenge for the project. CKD/CCKD can have different compositions of chemical components, therefore, the addition of CKD/CCKD to soil samples can have different impacts if the composition of CKD/CCKD is not consistent, which can affect the obtained data for the project. This problem can be mitigated by using the same type of soil throughout the project.

### **1.4.2 Soil Variability**

The composition of a soil sample is also a challenge for this project. Even when the same type of soil will be used throughout the project for testing, the results obtained may not be the same for each soil sample as soil samples can have different compositions of chemical components. This problem can be minimized by using the same type of soil throughout the project.

### **1.4.3 Laboratory Soils Testing**

The consistency of data obtained from soils testing is a challenge for the project. The test on soils can produce different data even when using the same procedure on the same sample. To mitigate this problem, the team will conduct a minimum of three trials on each sample and average the results.

## **1.5 Stakeholders**

The stakeholders of this project are the client, cement manufacturing companies, construction companies and the global community. Each of the stakeholders will have a stake in the outcome of this project.

### **1.5.1 The Client**

Professor Alarick Reiboldt, Civil and Environmental Engineering Instructor at Northern Arizona University, is the client who requested for the project. This project will provide him more information for his research on CCKD.

### **1.5.2 Cement Manufacturing Companies**

Cement manufacturing companies will benefit from the obtaining of CKD as CKD is currently listed as a by-product of the cement manufacturing process.



### 1.5.3 Construction Companies

Construction companies will be the ones using the product (CCKD) if CCKD proves to be a good stabilizer for soils.

### 1.5.4 Global Community

The production of CCKD will reduce the amount of CO<sub>2</sub> created by the cement manufacturing process. Therefore, the global community can benefit from the reduction of CO<sub>2</sub> in the atmosphere.

## 1.6 Scope of Services

This section of the proposal describes the work that the project team will conduct to implement the project and meet the client's needs to complete the study on Carbonated Cement Kiln Dust (CCKD) as a soil stabilization amendment. The team will have 6 main tasks to be done as shown below.

### **Task 1.0: Literature Review**

A literature review will provide the team with a deeper understanding of key points prior to working on the project. The literature review helps the team determine an experimental design for the project based on previous studies.

### **Task 2.0: Soil Selection**

#### ***Task 2.1: Determining Soil Used***

The data obtained from soil testing is usually not consistent. The composition of a soil sample is a challenge to the project. Even when same procedures of testing will be used throughout the project, the results obtained may not be the same for each soil sample as soil samples can have different compositions of chemical components. Therefore, the team will decide on what type of soil shall be used throughout this project to mitigate the errors obtained in soil testing. Because there are several previous studies on the use of lime, Class C Fly Ash and Cement Kiln Dust (CKD) as soil stabilizers, the team will contact the people who studied this case to determine what type of soil is most fitted for the project. By knowing the classification of soil that has been used in previous studies, the team can conduct testing on a similar type of soil and verify the obtained results with the results from previous studies.

#### ***Task 2.2: Obtaining Soil Samples***

After determining what type of soil is most fitted for this project, the team will develop similar soil samples that belong to the same classification as the soil samples used in previous studies for this project. By using the same type of soils studied previously, the team may be able to mitigate the errors made when conducting technical works. The team will also have a basis to compare the tests' results to. Soil samples will be obtained from sites that are located within Flagstaff, Arizona.

### ***Task 2.3: Soil Classification***

The project team will conduct soil classification to determine if the soils obtained from sites belong to the same classification as mentioned above. To determine the classification of soil samples, the project team will conduct sieve analysis according to ASTM D421 to obtain the particle size distribution of soil samples, and Atterberg limit tests according to ASTM D4318-10e1 to obtain the Atterberg limits of soil (liquid limit and plastic limit). After knowing the particle size distribution and Atterberg limits of soil samples, the project team will analyze the results to determine if the obtained soil samples belong to the desired classification. Testing process will be done until the project team obtained the desired classification.

### **Task 3.0: Preparing Soil Samples**

#### ***Task 3.1: Determining Amount of Mixtures***

Based on previous studies, to determine the efficacy of CCKD as a stabilizer for soils, the team will prepare a minimum of 10 different soil mixtures. The type of soil used for this project shall be based on the previous study, which belongs to Port series and is classified as CL-ML with a liquid limit of approximately 27% and a plasticity index of approximately 5% [4]. One of the specimen will be prepared without the addition of lime, CKD and CCKD; and used for control. Other 9 mixtures will be prepared for the project by adding a specific amount of lime (3, 7, or 10%), CKD (5, 10 or 15%) and CCKD (9, 18 or 28%) to the raw soil. The mixture plan can be found in Table 1.1 below.

**Table 1.1: Mixture Plan**

Mixture	Control	L1	L2	L3	CKD1	CKD2	CKD3	CCKD1	CCKD2	CCKD3
Lime	-	3.42%	6.84%	10.27%	-	-	-	-	-	-
CKD	-	-	-	-	5%	10%	15%	-	-	-
CCKD	-	-	-	-	-	-	-	9.18%	18.36%	27.54%
Soil	100%	96.58%	93.16%	89.73%	95%	90%	85%	90.82%	81.64%	72.46%

#### ***Task 3.2: Obtaining Lime, CKD and CCKD***

The amounts of Lime, CKD and CCKD obtained for the Capstone Project will be in accordance with the experimental plan explained above.

#### ***Task 3.3: Preparing Soil Mixtures***

After obtaining Lime, CKD and CCKD, the project team will prepare the mixtures in accordance with the experimental plan explained above. Each amount of additive including the control will be prepared with 3 samples to ensure that the data is consistent between tests. The results of these tests before and after adding cement, CKD and CCKD will then be compared to determine the efficacy of CCKD as a soil stabilization amendment. Additional tests and statistical analysis will be considered in case that the obtained data is not consistent.

#### **Task 4.0: Soil Strength Test**

The following tests are necessary to determine the shear strength of soils: Direct Shear and Triaxial Shear Test (Unconsolidated Undrained Test). By obtaining the parameters that measure soil strength, the team will be able to determine if CCKD can help increase the strength of soil samples.

##### ***Task 4.1: Proctor Compaction Tests***

The project team will conduct Proctor Compaction Test in accordance with ASTM D698 to determine optimum moisture content and maximum dry unit weight of soil samples.

##### ***Task 4.2: Direct Shear Test***

The project team will conduct Direct Shear Test based on ASTM D3080 to obtain the data of shear stress to horizontal displacement and shear stress to normal stress to determine peak shear strengths, effective cohesions and effective friction angles of soil samples.

##### ***Task 4.3: Triaxial Shear Test***

The project team will conduct Triaxial Test (Unconsolidated Undrained Test) based on ASTM D2850-03a to determine undrained shear strength of the soil sample.

#### **Task 5.0: Analysis Results**

The team will analyze obtained results from the testing process to obtain the desired properties of soil samples using statistical methods according to each test. The analyzing process will be conducted along with the testing process. The team will compare the results after each test to ensure that there is no mistake in results, and that the team will have enough time to redo the tests in case mistake occurs. After obtaining the desired properties of all soil samples, the team will compare the results of conducted tests with previous studies' results to determine if CKD/CCKD can be used as soil amendment.

#### **Task 6.0: Project Management**

To ensure quality deliverables of the results on time, the project team will conduct the following tasks for project management.

##### ***Task 6.1: Scheduling***

The project team estimates the time each task will take. The estimated duration, start date and end date of each task are shown in Table 1.2 below.

**Table 1.2: Project Schedule**

<b>Tasks</b>	<b>Start Date</b>	<b>End Date</b>
<b>1.0 Literature Review</b>	Jan 16	Jan 29
<b>2.0 Soil Selection</b>	Jan 30	Feb 19
2.1 Determining Soil Used	Jan 30	Feb 5
2.2 Obtaining Soil Samples	Feb 6	Feb 12
2.3 Soil Classification	Feb 13	Feb 19
<b>3.0 Preparing Soil Samples</b>	Feb 20	Feb 26
3.1 Determining Amount of Mixtures	Feb 20	Feb 26
3.2 Obtaining lime, CKD and CCKD	Feb 20	Feb 26
3.3 Preparing Soil Mixtures	Feb 20	Feb 26
<b>4.0 Soils Testing</b>	Feb 27	Apr 9
4.1 Proctor Compaction Tests	Feb 20	Feb 26
4.2. Direct Shear Tests	Feb 27	Mar 19
4.3. Triaxial Shear Tests	Mar 20	Apr 9
<b>5.0 Analysis Results</b>	Apr 10	Apr 23
<b>6.0 Project Management</b>	Jan 16	May 5

Each task shall take certain duration as shown in Table 1.2. For Project Management, the project team will create a schedule at the start of the project. To ensure quality deliverables of the results on time, the team will conduct meeting once a week during the project duration. Therefore, project management tasks last throughout the project duration (approximately 4 months).

***Task 6.2: Meetings***

The team will have at least one team meeting every week to discuss tasks, and at least one meeting with the client every two weeks to report the results and plans for the tasks to follow. When conducting technical work, the team shall meet up with the technical advisor to ask for advices before conducting a new type of test.

***Task 6.3: Deliverables***

The team will document all the works done and compare with the schedule to ensure that the tasks are finished on time. The results of this project may also result in a published journal article. All deliverables will be delivered to the client by the end of CENE486 course.

**1.7 Exclusions**

The project team will only take responsibility to deliver work for the tasks listed in the Scope of Work for this project. The team will not take responsibility to finish work outside of this scope. Additional tasks will be considered if the tasks deem necessary for the project and approved by the client.

## 2.0 Technical Sections

This section of the 50% design report provides the details of work done by the team to obtain the desired results based on the project team's scope of work.

### 2.1 Literature Review

The soils used in the previous study on Engineering Properties and Moisture Susceptibility of Silty Clay Stabilized with Lime, Class C Fly Ash (CFA), and Cement Kiln Dust by professor Pranshoo Solanki from Illinois State University have a percent finer than sieve #200 of 94% (94% fines), a liquid limit of 27% and a plasticity index of 5%. According to Unified Soil Classification System (USCS), for soils with 50% or more fines, the soils used in previous study are classified as CL-ML Sandy Silty Clay. Table 2.1 below summarizes all necessary information regarding the soils used in previous study.

**Table 2.1: Information on Soils used in Previous Study [4]**

Method	Parameter/units	Value
ASTM D 2487	USCS Symbol	CL-ML
ASTM D 2487	% finer than 0.075 mm	83
ASTM D 422	% finer than 0.002 mm	11
ASTM D 4318	Liquid limit (%)	27
ASTM D 4318	Plasticity index (%)	5
ASTM D 854	Specific gravity	2.65
ASTM D 698	Optimum moisture content (%)	13.1
ASTM D 698	Max. dry unit weight (kN/m <sup>3</sup> )	17.8
ASTM D 6276	pH	8.91

Note: USCS=Unified Soil Classification System.

A total of 40 specimens were prepared for previous study by adding a specific amount of additive, namely, lime (3, 6 or 9%), CFA (5, 10, 15%), and CKD (5, 10 or 15%) to the raw soil. These amounts of additives were determined based on the dry weight of soil (17.8 kN/m<sup>3</sup>) as shown in Table 2.1. Prior to mixing, an amount of water based on the optimum moisture content of the raw soils was added to the specimens. Then, the mixture were compacted according to Proctor Compaction Tests. After compaction, specimens were cured in a humidity room having a temperature of 23.0 ± 1.7°C and a relative humidity of approximately 96% for 28 days for specimens to obtain maximum strength [4].

However, for this project, because of the tight schedule, the project team will not be able to cure the specimens for a duration of 28-day to test the specimens at full strength. Therefore, after discussing with the technical advisor for this Capstone project, Professor Alarick Reiboldt, the project team determined to cure the specimens for a 7-day period, as curing the specimens for 7 days will allow the specimens to reach a certain minimum degree of strength prior to testing [7].

## 2.2 Soil Selection


CL-ML Sandy Silty Clay (USCS Classification) is the type of soils that the project team decided to use for this Capstone project.

### 2.2.1 Determining Soil Used

The data obtained from soils testing is usually not consistent. The composition of a soil sample is a challenge to the project. Even when the same procedure for a test is used, the result will vary from sample to sample. By conducting testing on a similar type of soil and verify the obtained results with results obtained from previous study, the project team can mitigate the errors obtained in soil testing. Therefore, the project team decided to use soils that belong to the same USCS classification as the soils used in previous study (CL-ML Sandy Silty Clay).

### 2.2.2 Obtaining Soil Samples

Because CL-ML Sandy Silty Clay is not available in Flagstaff, the project team decided to look for locations with silt-rich sediment. The team decided on the location after contacting NAU Geology faculties. Figure 2.1 below shows the location where the project team obtained the soils.

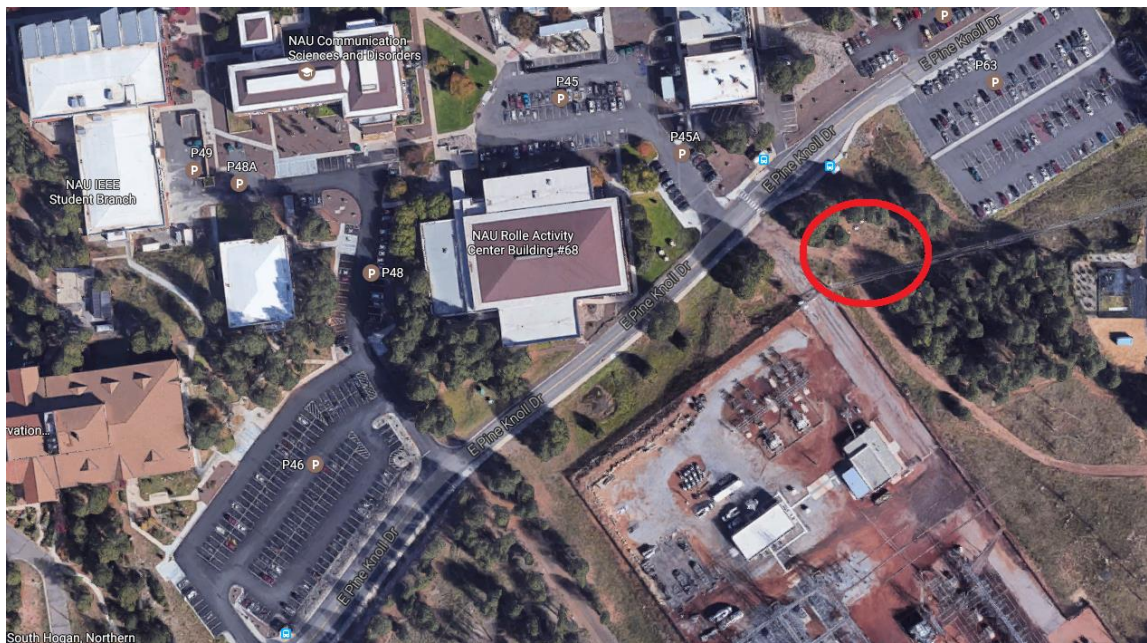

**Figure 2.1: Silt-Rich Sediment Site**

The location is located near NAU P63, close to E. Pine Knoll Dr. The team collected the soil three times. Each time, the team get over 50 kilograms of soils.

However, because the soils at this location do not belong to the same classification as soils used in previous study, the team had to engineer soils that belong to CL-ML Sandy Silty Clay classification by sieving. Through the sieving process, the project team was able to obtain approximately 35 kilograms of desired soils to use for this project.

## 2.2.3 Soil Classification

### 2.2.3.1 Sieve Analysis

Three (3) Sieve Analyses were conducted in accordance with ASTM D421 procedure to determine the percent finer of soils obtained from site. Data from Sieve Analysis can be found in Appendices A to C.

The original soil samples at site near NAU P63 have percent gravels of 22%, percent sands of 62% and percent fines of 16%. Table 2.2 below shows the average percent finer of each sieve.

Table 2.2: Average Percent Finer (PSD)

Sieve #	Sieve opening (mm)	Soil #1's % Finer	Soil #2's % Finer	Soil #3's % Finer	Average % Finer (AVG)
4	4.75	77.83	77.83	87.79	81.15
10	2	61.04	61.48	75.74	66.09
20	0.85	46.17	47.07	59.62	50.95
40	0.425	38.06	38.78	50.43	42.42
60	0.25	33.06	33.47	43.90	36.81
140	0.106	24.51	24.46	31.07	26.68
200	0.075	15.41	14.95	19.12	16.49
Pan	0.01	0.00	0.00	0.00	0.00

The average PSD graph is shown in Figure 2.2 below.

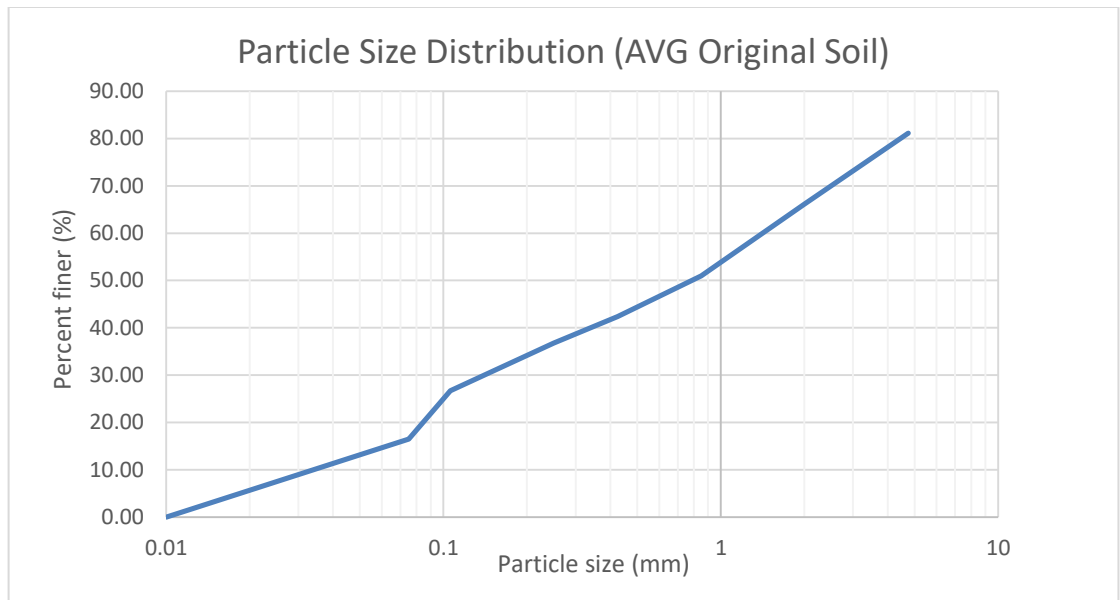


Figure 2.2: Average PSD Graph



### 2.2.3.2 Atterberg Limit Tests

Using soils retained on and passing through sieve #200, the project team conducted Atterberg Limit Tests in accordance with ASTM D4318-10e1. The soil samples have an average liquid limit of 29.4% and a plastic limit of 24.2%, resulting in a plasticity index of 5.2%.

Tables 2.3 and 2.4 below show the results of Atterberg Limit Tests. Refer to Appendix D for data obtained from Atterberg Limit Tests.

**Table 2.3: Average Liquid Limit**

Sample #	Liquid Limit (LL)
LL1	28.71
LL2	29.13
LL3	31.88
LL4	27.93
Average LL	29.41

**Table 2.4: Average Plastic Limit**

Sample #	Plastic Limit (PL)
PL1	24.59
PL2	23.90
PL3	26.32
PL4	23.31
PL5	23.93
PL6	24.19
PL7	23.64
PL8	23.95
Average PL	24.23

The average liquid limit and plasticity index obtained from Atterberg Limit Tests on soils obtained from the site are close to the limit values of the soils used in previous study (27% and 5%, accordingly).



### 2.2.3.3 Soil Classification

Based on the Sieve Analysis and Atterberg Limit Tests' Results, the USCS classification for soils obtained from the site is **SM Silty Sand**.


Therefore, the team decided to keep only soils retained and passing through sieve #200. 'Sand' portion of these samples includes soils that pass through sieve #140, resulting in a soil sample that have roughly 40% sand and 60% fines. The USCS classification for the engineered soils is **CL-ML Sandy Silty Clay**.

Table 2.5 below shows the average PSD of the engineered soils. Refer to Appendices E to G for data on Engineered Soils.

**Table 2.5: Engineered Soil's Average PSD**

Sieve #	Sieve Opening (mm)	Soil 1's % finer	Soil 2's % finer	Soil 3's % finer	AVG % Finer
140	0.106	100.00	100.00	100.00	100.00
200	0.075	62.86	61.14	61.54	61.85
Pan	0.01	0	0	0	0

Figure 2.3 shows the average PSD graph of the engineered soils.

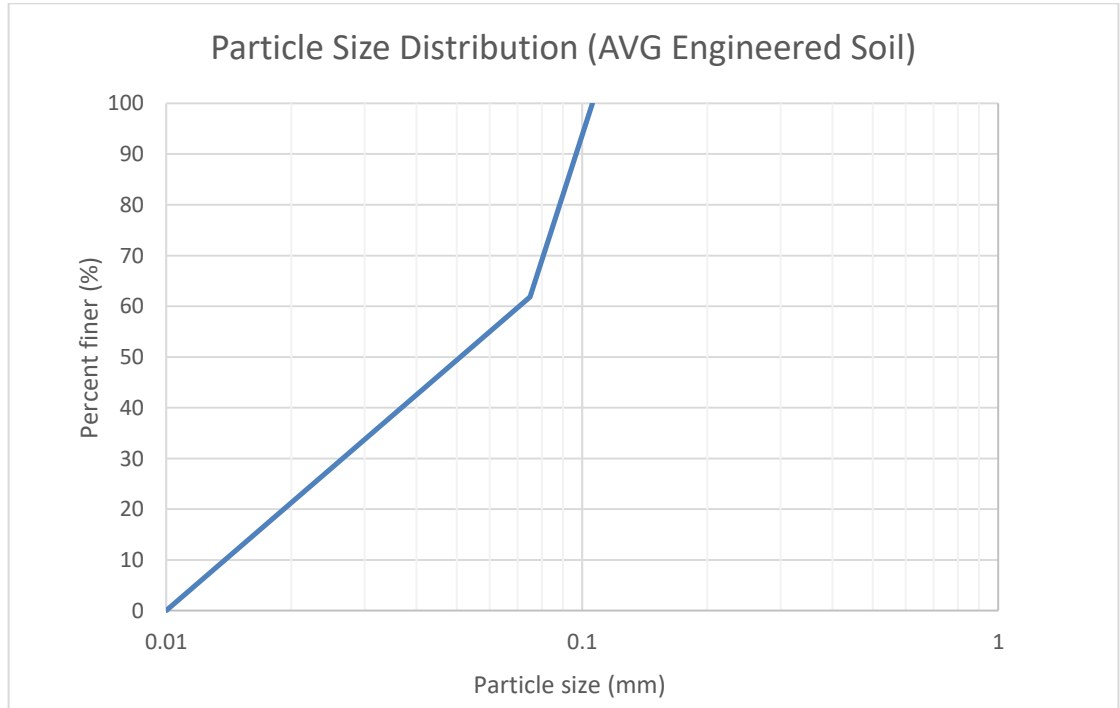

**Figure 2.3: Engineered Soil's Average PSD Graph**

## 2.3 Preparing Soil Mixtures

### 2.3.1 Determining Amount of Mixtures

To prepare soil mixtures, the team first determined the amount of additive that needs to be added to each sample before obtaining Lime, CKD and CCKD.

The engineered soils have a maximum dry unit weight of  $16.91 \text{ kN/m}^3$ , which is close to the maximum dry unit weight of the soils used in previous study. Therefore, the team decided to prepare CKD mixtures at 5, 10 and 15% like previous study.

For lime and CCKD mixtures, the amounts of lime and CCKD added to the mixtures were based on the percentage of Calcium Oxide (CaO) in the CKD provided. The chemical components of CKD are as shown in Table 2.6 below.

Table 2.6: CKD Chemical Components

CKD Chemical Components	SiO <sub>2</sub>	13.83%
	Al <sub>2</sub> O <sub>3</sub>	3.00%
	Fe <sub>2</sub> O <sub>3</sub>	1.54%
	CaO	64.72%
	MgO	0.82%
	SO <sub>3</sub>	5.31%
	Na <sub>2</sub> O	0.05%
	K <sub>2</sub> O	3.66%
	TiO <sub>2</sub>	0.17%
	Cl	1.47%
	LOI	5.43%
	<b>Total</b>	<b>100.00%</b>
	Fineness (Passing 200 M)	91.41%

As shown in Table 2.6, Calcium Oxide (CaO) is 64.72% of CKD. Therefore, for lime samples to have the same amount of CaO as CKD, the project team decided to mix lime samples based on the proportion of CaO in CKD (64.72% to 94.57%), which was calculated to be 68.44%. The percent admixtures for lime samples were then calculated to be 3.42, 6.84 and 10.27% accordingly to 5, 10 and 15% CKD mixtures.

For CCKD samples, the percent admixtures were determined based on the amount of CKD reacting with CO<sub>2</sub> to be 9.18%, 18.36% and 27.54%. Refer to Appendix H for the stoichiometry analysis of CKD.

Table 2.7 below shows the amount of lime, CKD and CCKD needed to add to obtain each mixture.

**Table 2.7: Amount of Lime, CKD and CCKD needed to add**

Mixture	% Admixture	% Soil	Soil Amount (kg)	Mixture Amount (kg)	lime/CKD/CCKD Amount (kg)
Lime 1	3.42%	96.58%	3	3.10629	0.10629
Lime 2	6.84%	93.16%	3	3.22039	0.22039
Lime 3	10.27%	89.73%	3	3.34319	0.34319
CKD 1	5.00%	95.00%	3	3.15789	0.15789
CKD 2	10.00%	90.00%	3	3.33333	0.33333
CKD 3	15.00%	85.00%	3	3.52941	0.52941
CCKD 1	9.18%	90.82%	3	3.30319	0.30319
CCKD 2	18.36%	81.64%	3	3.67456	0.67456
CCKD 3	27.54%	72.46%	3	4.14001	1.14001

### 2.3.2 Obtaining Lime, CKD and CCKD

The total amounts of lime, CKD and CCKD needed are as shown in Table 2.8 below. These values were calculated based on the percent of lime (CaO) in CKD and CCKD.

**Table 2.8: Total Amounts Needed**

Total Lime	0.66987 kg
Total CKD	1.02064 kg
Total CCKD	2.11777 kg

The project team was able to obtain lime from lab manager Gerjen Slim; and CKD and CCKD from Professor Alarick Reiboldt.

### 2.3.3 Preparing Soil Mixtures

Soil Mixtures were prepared in accordance with the values mentioned in Tables 2.7 and 2.8 above. Prior to mixing, a certain amount of water (approximately 0.52 kg) based on the soils' Optimum Moisture Content of 17.43% of raw soils) was added to the samples. All mixtures were packed and will be left for a period of 7-day to ensure the components mix well together.

## 2.4 Soils Testing

After conducting Proctor Compaction Tests in accordance with ASTM D698-91 and preparing soil mixtures, the team will conduct at least three (3) Direct Shear Tests and three (3) Triaxial Shear

Tests on each mixture. The project team started testing process for control samples on February 25, 2017. Summary of results from a minimum of 60 laboratory tests are to be expected at the end of this semester.

#### 2.4.1 Proctor Compaction

The project team conducted 3 trials of Proctor compaction tests in accordance with ASTM D698-91. Refer to Appendices I to K for data from each trial. Table 2.9 below shows the average values of optimum moisture content and maximum dry unit weight.

**Table 2.9: Proctor Tests' Results**

Proctor Compaction Test #	1	2	3
OMC (%)	16.20	18.98	17.10
Max Dry UW (kN/m <sup>3</sup> )	17.45	16.54	16.74
AVG OMC	17.43 %		
AVG MDUW	16.91 kN/m <sup>3</sup>		

#### 2.4.2 Direct Shear

Work In Progress

#### 2.4.3 Triaxial Shear: Unconsolidated Undrained

Work In Progress

### 2.5 Analysis Results

Results from Direct Shear and Triaxial Shear Tests will be analyzed and discussed in this section.

### 2.6 Project Management

The project team has been preparing all deliverables to meet the schedules of CENE486C-1 Spring 2017. These deliverables include 50% Design Report, Project Status Presentations (1 & 2), and Project Status Meetings.

Aside from Project Deliverables, the team also meets up and discusses every week to ensure the project tasks are delivered on time with quality.

### 3.0 References

- [1] M. Rubenstein, "Emissions from the Cement Industry", Blogs.ei.columbia.edu, 2016. [Online]. Available: <http://blogs.ei.columbia.edu/2012/05/09/emissions-from-the-cement-industry/>. [Accessed: 11- Dec- 2016].
- [2] D. Little, "EVALUATION OF STRUCTURAL PROPERTIES OF LIME STABILIZED SOILS AND AGGREGATES", 2016. [Online]. Available: [http://www.lime.org/documents/publications/free\\_downloads/soilsaggregates-vol1.pdf](http://www.lime.org/documents/publications/free_downloads/soilsaggregates-vol1.pdf). [Accessed: 03- Oct- 2016].
- [3] R. Parsons and E. Kneebone, "Use of Cement Kiln Dust for the Stabilization of Soils", Geotechnical Engineering for Transportation Projects, 2004.
- [4] P. Solanki, N. Khoury and M. Zaman, "Engineering Properties and Moisture Susceptibility of Silty Clay Stabilized with Lime, Class C Fly Ash, and Cement Kiln Dust", J. Mater. Civ. Eng., vol. 21, no. 12, pp. 749-757, 2009. 1.3.2.1
- [5] R. D. Holtz and W. D. Kovacs, An introduction to geotechnical engineering. Englewood Cliffs, NJ, United States: Prentice-Hall, 1981.
- [6] S. Rees, "Introduction to Triaxial Testing", GDS Instruments, 2016. [Online]. Available: [http://www.gdsinstruments.com/\\_\\_assets\\_\\_/pagepdf/000037/Part%201%20Introduction%20to%20triaxial%20testing.pdf](http://www.gdsinstruments.com/__assets__/pagepdf/000037/Part%201%20Introduction%20to%20triaxial%20testing.pdf). [Accessed: 19- Sep- 2016].
- [7] EB001, "Design and Control of Concrete Mixtures", 2017. [Online]. Available: [http://www.ce.memphis.edu/1101/notes/concrete/PCA\\_manual/Chap12.pdf](http://www.ce.memphis.edu/1101/notes/concrete/PCA_manual/Chap12.pdf). [Accessed: 01- Mar- 2017].

## 4.0 Appendices

### Appendix A: Sieve Analysis's Data on Raw Soil #1

Table 4.1: Data Soil #1

Sieve #	Sieve opening	Mass of sieve, A	Mass of sieve and	Mass of sample, $W_n$	Percent of mass	Cumulative percent $\sum R_n$	Percent finer, $(100 - \sum R_n)$
4	4.75	513.8	624.6	110.8	22.17	22.17	77.83
10	2	438.5	522.4	83.9	16.79	38.96	61.04
20	0.85	413.6	487.9	74.3	14.87	53.83	46.17
40	0.425	399.1	439.6	40.5	8.10	61.94	38.06
60	0.25	346.4	371.4	25	5.00	66.94	33.06
140	0.106	339	381.7	42.7	8.55	75.49	24.51
200	0.075	319.1	364.6	45.5	9.11	84.59	15.41
Pan	0.01	366.6	443.6	77	15.41	100.00	0.00
$\Sigma$	xx	xx	Xx	499.7	100		

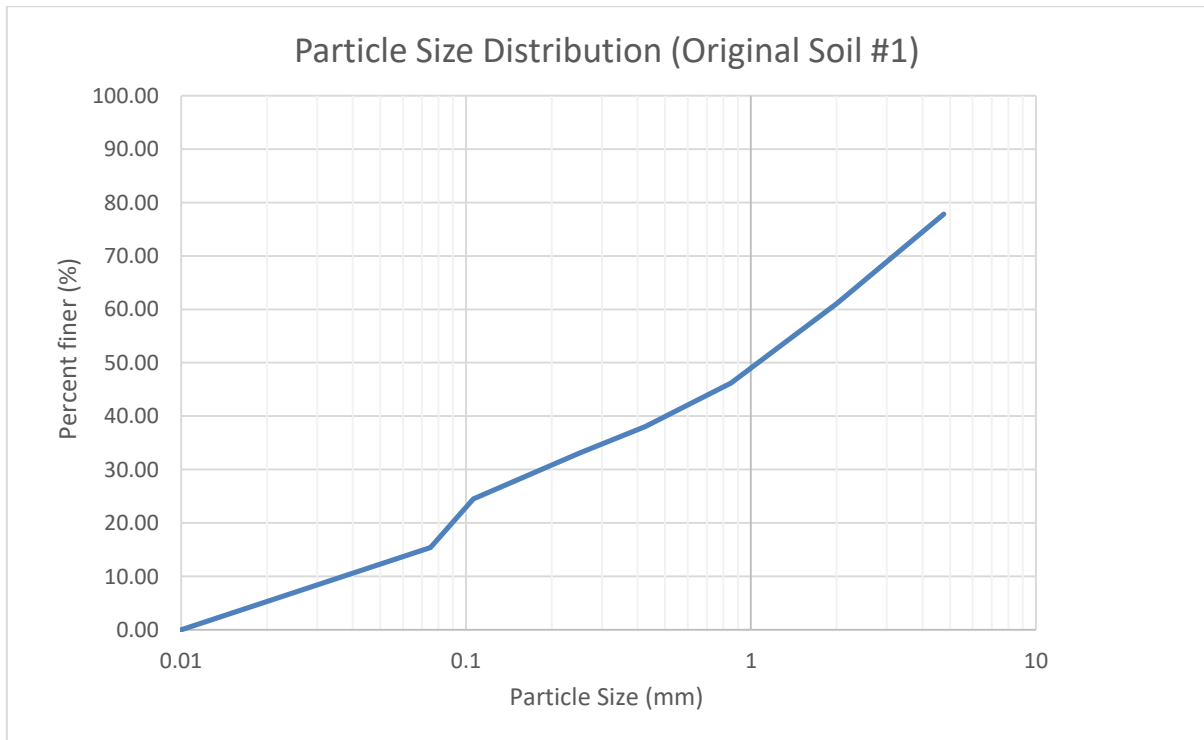


Figure 4.1: PSD Soil #1

## Appendix B: Sieve Analysis's Data on Raw Soil #2

Table 4.2: Data Soil #2

Sieve #	Sieve opening	Mass of sieve, A	Mass of sieve and	Mass of sample,	Percent of mass	Cumulative percent $\sum R_n$	Percent finer, $(100 - \sum R_n)$
4	4.75	513.8	625.3	111.5	22.17	22.17	77.83
10	2	438.5	520.7	82.2	16.35	38.52	61.48
20	0.85	413.6	486.1	72.5	14.42	52.93	47.07
40	0.425	399.1	440.8	41.7	8.29	61.22	38.78
60	0.25	346.4	373.1	26.7	5.31	66.53	33.47
140	0.106	339	384.3	45.3	9.01	75.54	24.46
200	0.075	319.1	366.9	47.8	9.50	85.05	14.95
Pan	0.01	366.6	441.8	75.2	14.95	100.00	0.00
$\Sigma$	xx	xx	xx	502.9	100		

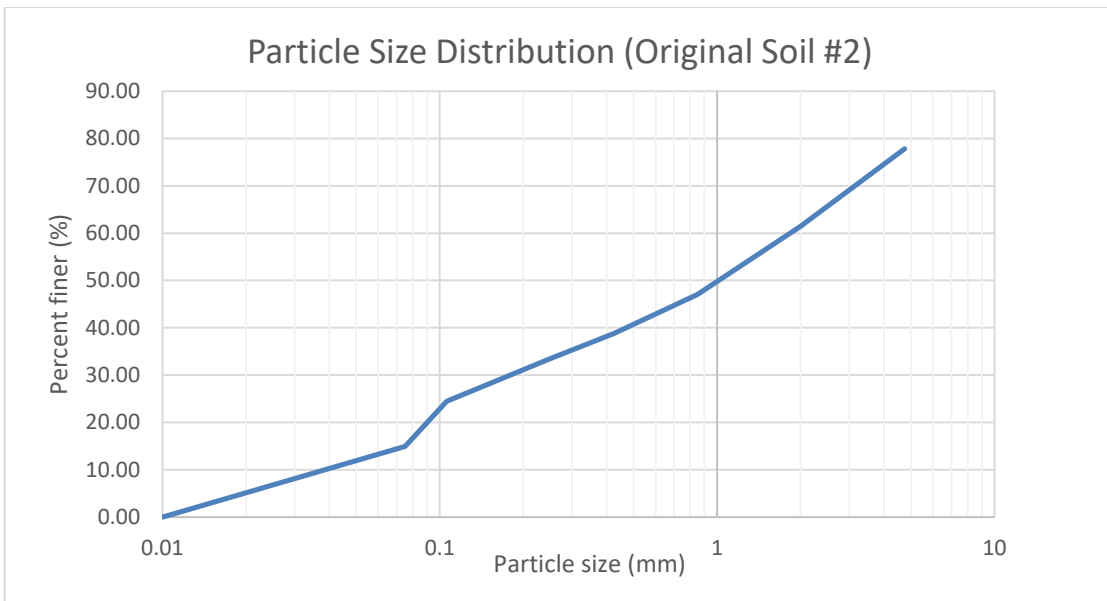


Figure 4.2: PSD Soil #2

## Appendix C: Sieve Analysis's Data on Raw Soil #3

Table 4.3: Data Soil #3

Sieve #	Sieve opening	Mass of sieve, A	Mass of sieve and	Mass of sample,	Percent of mass	Cumulative percent $\sum R_n$	Percent finer, $(100 - \sum R_n)$
4	4.75	732.3	793.4	61.1	12.21	12.21	87.79
10	2	450.1	510.4	60.3	12.05	24.26	75.74
20	0.85	416.1	496.8	80.7	16.12	40.38	59.62
40	0.425	361.2	407.2	46	9.19	49.57	50.43
60	0.25	372.4	405.1	32.7	6.53	56.10	43.90
140	0.106	338.8	403	64.2	12.83	68.93	31.07
200	0.075	341.4	401.2	59.8	11.95	80.88	19.12
Pan	0.01	370.4	466.1	95.7	19.12	100.00	0.00
$\Sigma$	xx	xx	xx	500.5	100		

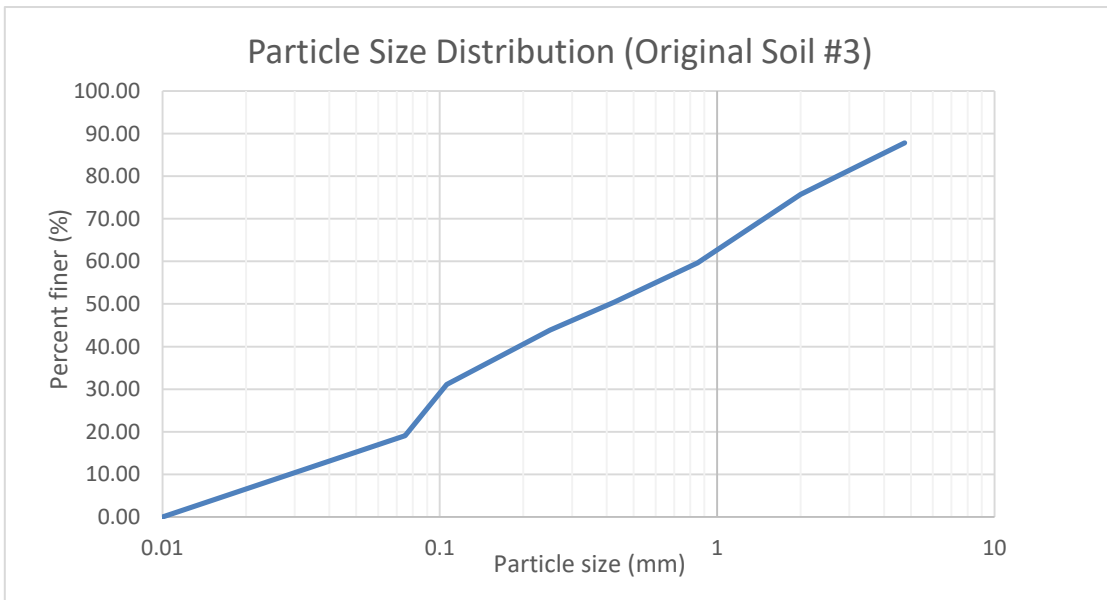


Figure 4.3: PSD Soil #3



## Appendix D: Atterberg Limit Tests' Data

Table 4.4: Plastic Limit Data

Can	Wcan	Wmoist	Wdry	Wm-Wd	Wd-Wc	PL
1	11.99	16.55	15.65	0.9	3.66	24.59
2	11.73	14.27	13.78	0.49	2.05	23.90
3	11.66	13.1	12.8	0.3	1.14	26.32
4	11.57	14.85	14.23	0.62	2.66	23.31
5	15.66	17.68	17.29	0.39	1.63	23.93
6	12.58	14.12	13.82	0.3	1.24	24.19
7	11.46	12.82	12.56	0.26	1.1	23.64
8	11.87	14.82	14.25	0.57	2.38	23.95
				Average	PL =	<b>24.23</b>

Table 4.5: Liquid Limit Data

Can	Wcan	Wmoist	Wdry	Wm-Wd	Wd-Wc	w	N	LL
1	31.12	35.2	34.29	0.91	3.17	28.71	25	28.71
2	22.5	30.9	28.99	1.91	6.49	29.43	23	29.13
3	22.3	28.8	27.25	1.55	4.95	31.31	29	31.88
4	22.7	30.6	28.91	1.69	6.21	27.21	31	27.93
							Average	LL = <b>29.41</b>

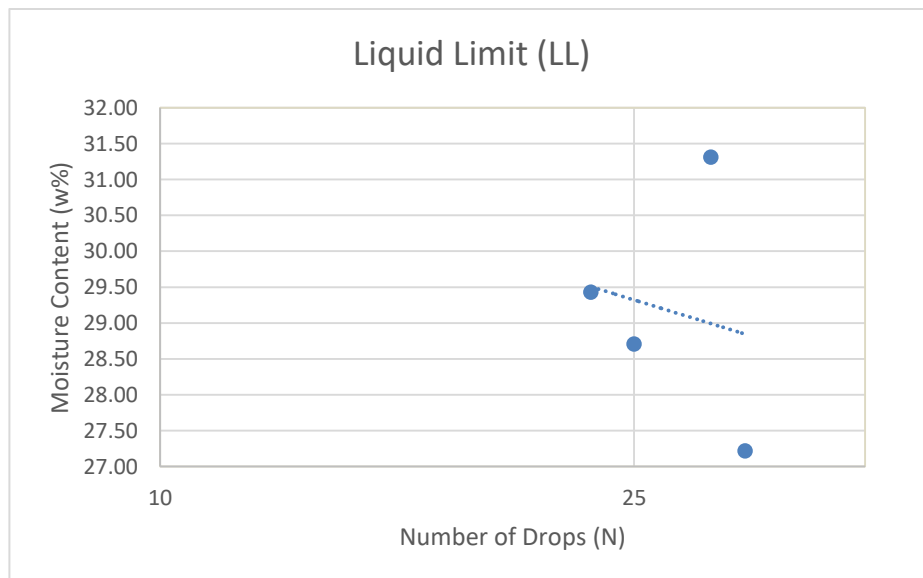


Figure 4.4: Liquid Limit Graph

## Appendix E: Engineered Soil #1

Table 4.6: Engineered Soil #1

Sieve #	Sieve opening (mm)	Mass of sieve, A (g)	Mass of sieve and retained sample, B (g)	Mass of sample, $W_n$ (g)	Percent of mass retained, $R_n$	Cumulative percent retained	Percent finer
140	0.106	n/a	n/a	0	0.0	0.0	100.0
200	0.075	319.1	364.6	45.5	37.1	37.1	62.9
Pan	0.01	366.6	443.6	77	62.9	100.0	0.0
Sum	xx	xx	xx	122.5	100		

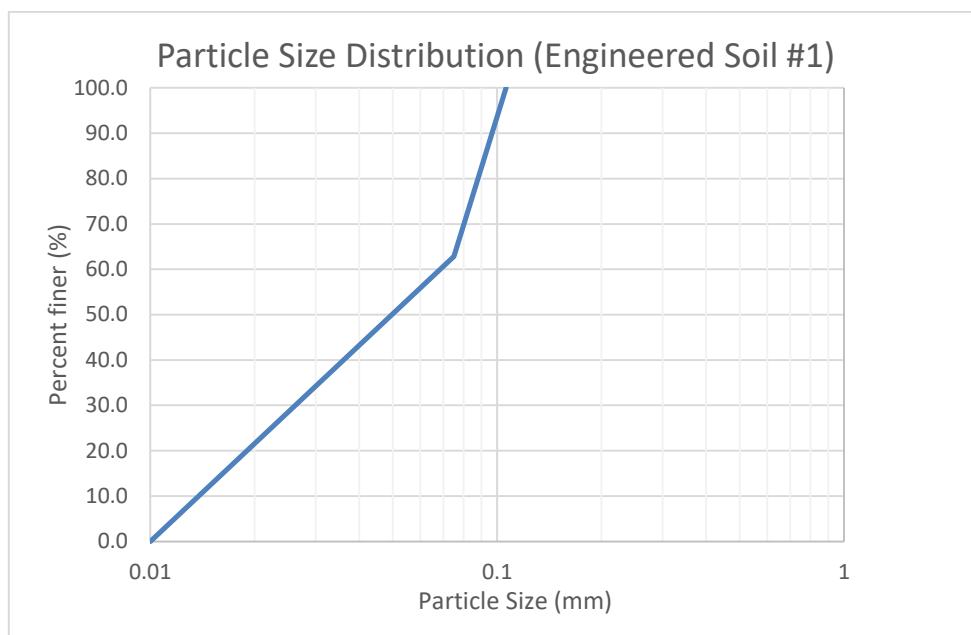


Figure 4.5: PSD Engineered Soil #1

## Appendix F: Engineered Soil #2

Table 4.7: Engineered Soil #2

Sieve #	Sieve opening (mm)	Mass of sieve, A (g)	Mass of sieve and retained sample, B (g)	Mass of sample, $W_n$ (g)	Percent of mass retained, $R_n$	Cumulative percent retained	Percent finer
140	0.106	339	384.3	45.3	0.0	0.0	100.0
200	0.075	319.1	366.9	47.8	38.9	38.9	61.1
Pan	0.01	366.6	441.8	75.2	61.1	100.0	0.0
SUM	xx	xx	xx	123	100		

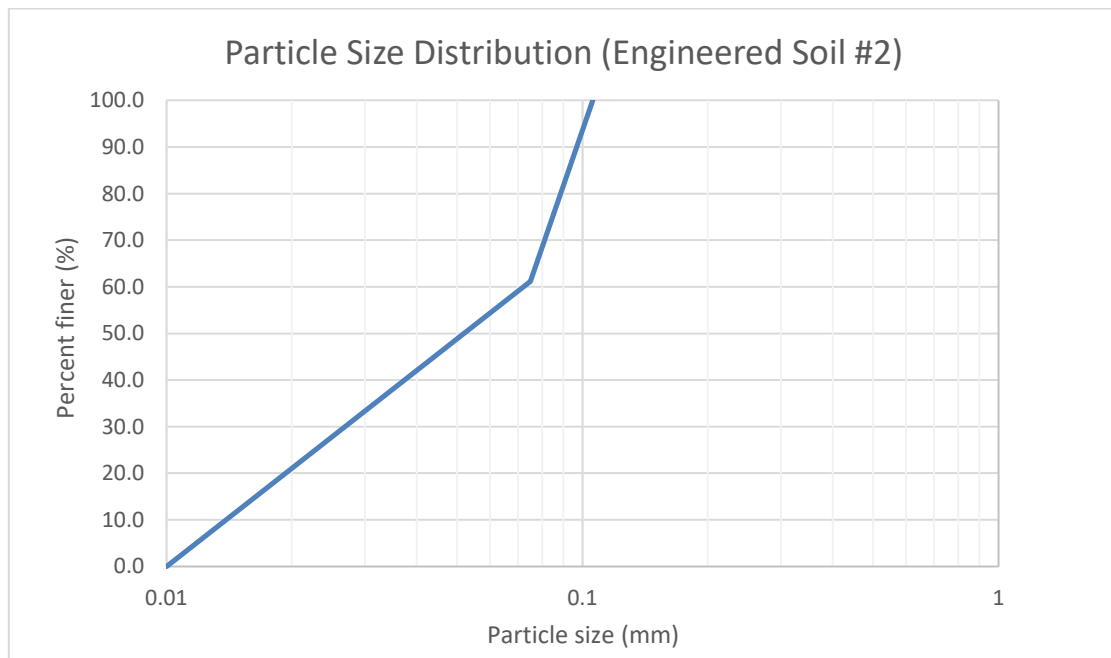


Figure 4.6: PSD Engineered Soil #2

## Appendix G: Engineered Soil #3

Table 4.8: Engineered Soil #3

Sieve #	Sieve opening (mm)	Mass of sieve, A (g)	Mass of sieve and retained sample, B (g)	Mass of sample, $W_n$ (g)	Percent of mass retained, $R_n$	Cumulative percent retained	Percent finer
140	0.106	338.8	403	0	0	0	100
200	0.075	341.4	401.2	59.8	38.46	38.46	61.54
Pan	0.01	370.4	466.1	95.7	61.54	100.00	0.00
SUM	xx	xx	xx	155.5	100		

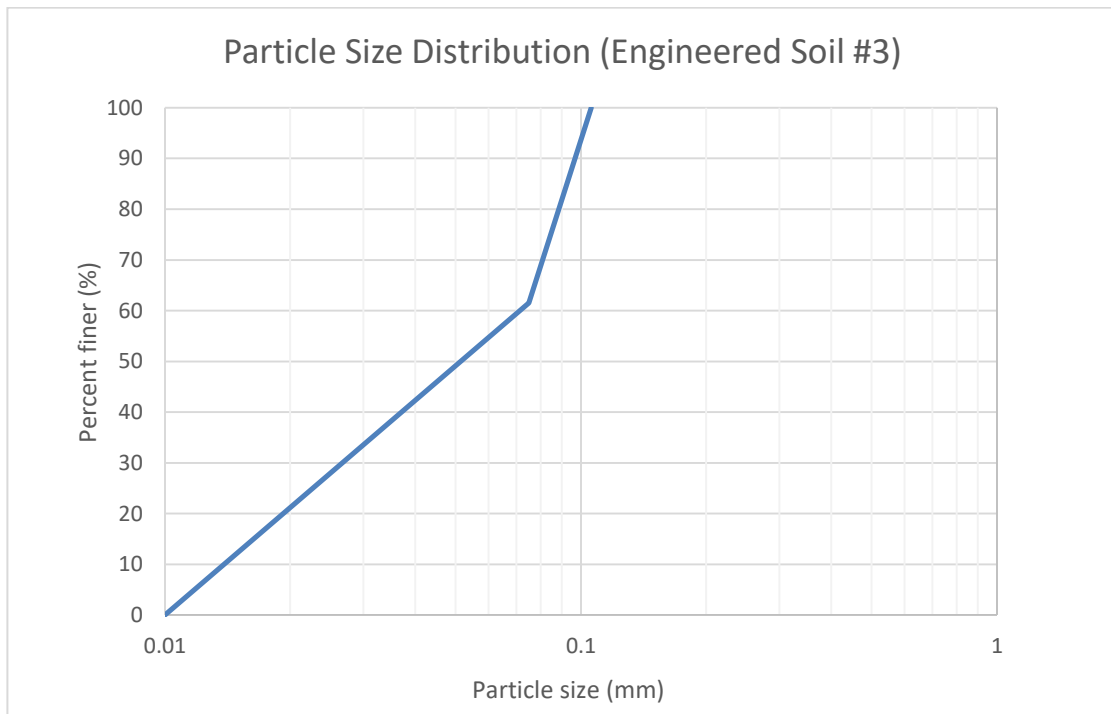


Figure 4.7: PSD Engineered Soil #3

## Appendix H: Stoichiometry Analysis

Table 4.9: Stoichiometry Analysis

CKD		94.57 g CKD	Molar Mass (g/mol)	mol/ 94.57g CKD	Reactions with CO <sub>2</sub>	Results	Molar Mass (g/mol)	mol from 94.57 g CKD	Mass (g)
SiO <sub>2</sub>	13.83%	13.83g	60.08	0.2302	SiO <sub>2</sub> +2CO <sub>2</sub> ->	Si(CO <sub>3</sub> ) <sub>2</sub>	148.10	0.23018	34.09
Al <sub>2</sub> O <sub>3</sub>	3.00%	3g	101.96	0.0294	Al <sub>2</sub> O <sub>3</sub> +3CO <sub>2</sub> ->	Al <sub>2</sub> (CO <sub>3</sub> ) <sub>3</sub>	233.99	0.02942	6.88
Fe <sub>2</sub> O <sub>3</sub>	1.54%	1.54g	159.69	0.0096	Fe <sub>2</sub> O <sub>3</sub> +3CO <sub>2</sub> ->	Fe <sub>2</sub> (CO <sub>3</sub> ) <sub>3</sub>	291.71	0.00964	2.81
CaO	64.72%	64.72g	56.08	1.1541	CaO+CO <sub>2</sub> ->	CaCO <sub>3</sub>	100.09	1.15413	115.51
MgO	0.82%	0.82g	40.30	0.0203	MgO+CO <sub>2</sub> ->	MgCO <sub>3</sub>	84.31	0.02035	1.72
SO <sub>3</sub>	5.31%	5.31g	80.06	0.0663	SO <sub>3</sub> +CO <sub>2</sub> ->	N/A (SO <sub>3</sub> )	80.06	0.06632	5.31
Na <sub>2</sub> O	0.05%	0.05g	61.98	0.0008	Na <sub>2</sub> O+CO <sub>2</sub> ->	Na <sub>2</sub> CO <sub>3</sub>	105.99	0.00081	0.09
K <sub>2</sub> O	3.66%	3.66g	94.20	0.0389	K <sub>2</sub> O+CO <sub>2</sub> ->	K <sub>2</sub> CO <sub>3</sub>	138.20	0.03886	5.37
TiO <sub>2</sub>	0.17%	0.17g	79.87	0.0021	TiO <sub>2</sub> +2CO <sub>2</sub> ->	Ti(CO <sub>3</sub> ) <sub>2</sub>	167.88	0.00213	0.36
Cl	1.47%	1.47g	35.45	0.0415	Cl+CO <sub>2</sub> ->	N/A (Cl)	35.45	0.04146	1.47
LOI	5.43%								
<b>Total</b>	<b>100.00 %</b>	94.57g						Total Mass (CCKD) from 94.57 g CKD =	173.61
Fineness (Passing 200 M)	91.41%						94.57 g CKD ->	173.61	g CCKD

## Appendix I: Proctor Test #1

Table 4.10: Proctor Test #1

Sample	m2 (g)	m1 (g)	MC (%)	V (m <sup>3</sup> )	W2 (kN)	W1 (kN)	UW Y (kN/m <sup>3</sup> )	Dry UW (kN/m <sup>3</sup> )
1	N/A	4255	0.62	n/A	N/A	0.04173	n/a	n/a
2	5895	4255	12.08	0.0009359	0.05782	0.04173	17.19	15.33
3	6092	4255	13.88	0.0009542	0.05974	0.04173	18.87	16.57
4	6194	4255	16.17	0.0009377	0.06074	0.04173	20.27	17.45
5	6161	4255	18.49	0.0009374	0.06042	0.04173	19.94	16.83
6	6131	4255	20.98	0.0009343	0.06013	0.04173	19.69	16.28

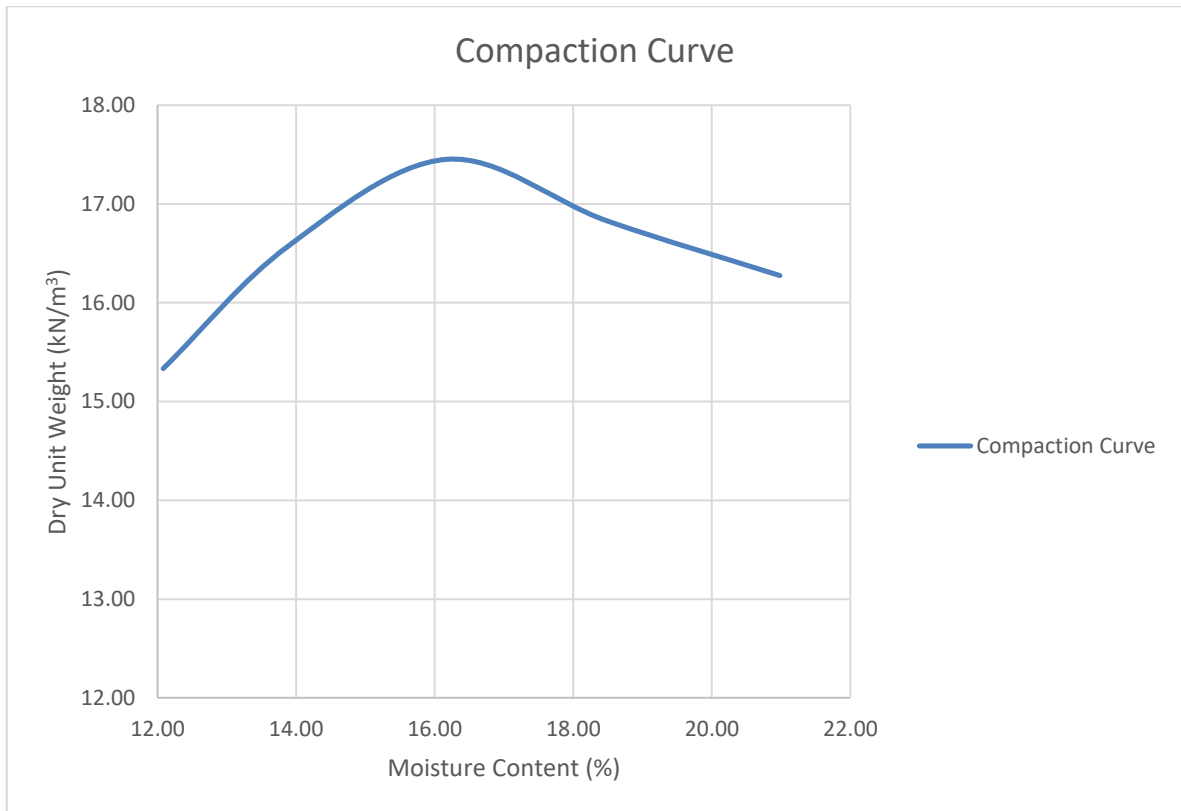


Figure 4.8: Compaction Curve #1

## Appendix J: Proctor Test #2

Table 4.11: Proctor Test #2

Sample	m2 (g)	m1 (g)	MC (%)	V (m <sup>3</sup> )	W2 (kN)	W1 (kN)	UW Y (kN/m <sup>3</sup> )	Dry UW (kN/m <sup>3</sup> )
1	6044	4255	16.12	0.0009367	0.05928	0.04173	18.73	16.13
2	6147	4255	17.01	0.0009719	0.06029	0.04173	19.09	16.32
3	6145	4255	19.36	0.0009390	0.06026	0.04173	19.74	16.54
4	6081	4255	23.20	0.0009232	0.05964	0.04173	19.40	15.75

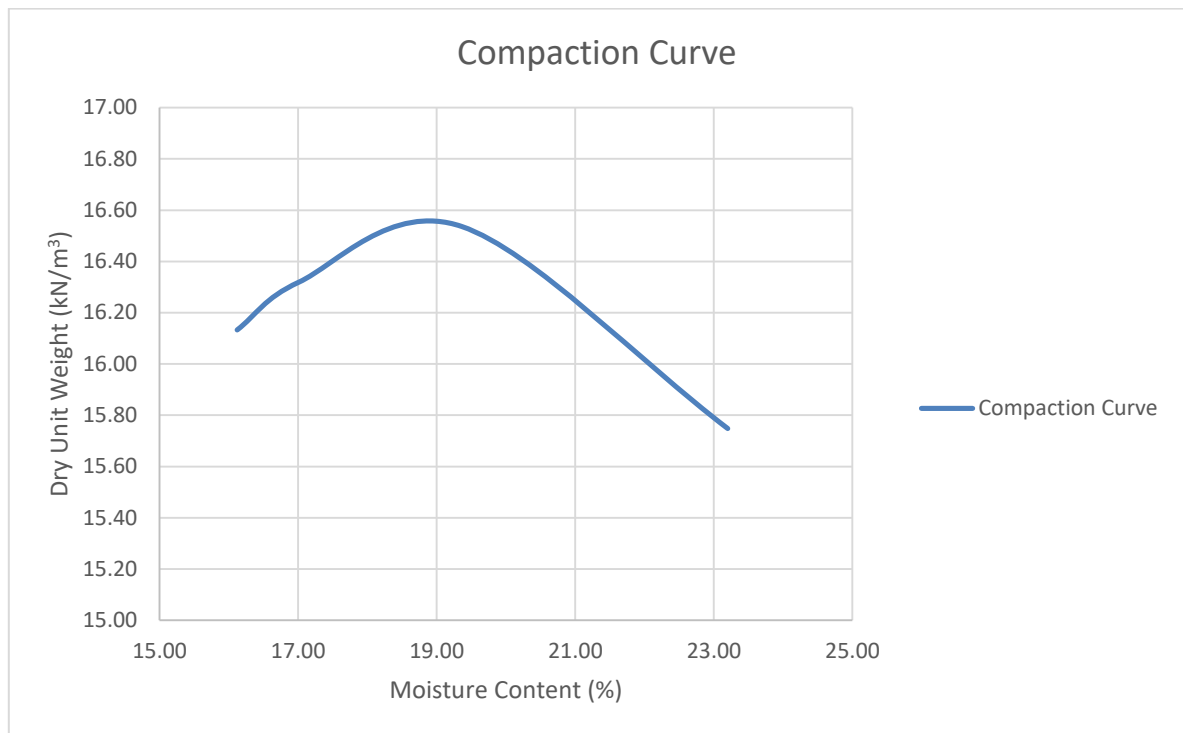


Figure 4.9: Compaction Curve #2

## Appendix K: Proctor Test #3

Table 4.12: Proctor Test #3

Sample	m2 (g)	m1 (g)	MC (%)	V (m <sup>3</sup> )	W2 (kN)	W1 (kN)	UW Y (kN/m <sup>3</sup> )	Dry UW (kN/m <sup>3</sup> )
1	6153	4291	14.85	0.0009656	0.06034	0.04208	18.90	16.46
2	6214	4291	17.22	0.0009610	0.06094	0.04208	19.62	16.74
3	6163	4291	19.20	0.0009644	0.06044	0.04208	19.04	15.97

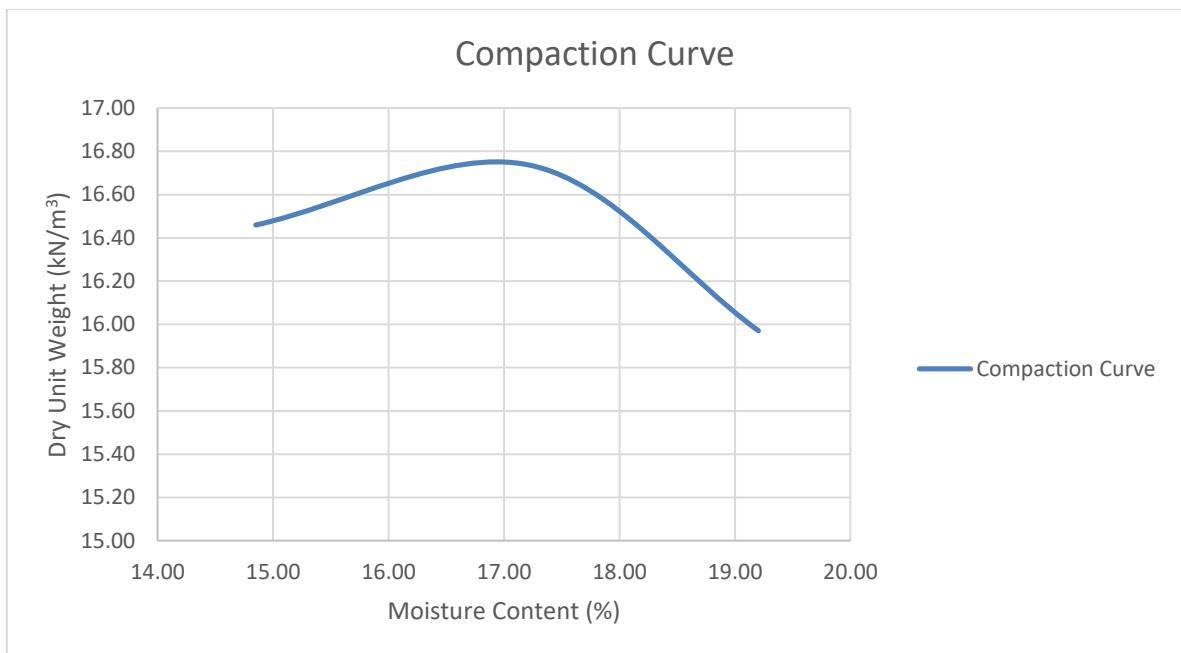


Figure 4.10: Compaction Curve #3